

Dissipation in Mesoscopic Superconductors with Ac Magnetic Fields

A. D. Hernández^{*,†}, O. Arés^{*}, C. Hart^{*}, D. Domínguez[†],
H. Pastoriza[†] and A. Butera[†]

^{*} Laboratorio de Superconductividad, Universidad de La Habana, Cuba

[†] Centro Atómico Bariloche, 8400 S. C. de Bariloche, Argentina

The response of mesoscopic superconductors to an ac magnetic field is investigated both experimentally and with numerical simulations. We study small square samples with dimensions of the order of the penetration depth. We obtain the ac susceptibility $\chi = \chi' + i\chi''$ at microwave frequencies as a function of the dc magnetic field H_{dc} . We find that the dissipation, given by χ'' , has a non monotonous behavior in mesoscopic samples. In the numerical simulations we obtain that the dissipation increases before the penetration of vortices and then it decreases abruptly after vortices have entered the sample. This is verified experimentally, where we find that χ'' has strong oscillations as a function of H_{dc} in small squares of Pb.

PACS: 74.78.Na, 74.25.Nf, 74.25.Ha.

The response of superconductors to an ac magnetic field has been of interest in the last years¹. The microwave surface impedance and the ac magnetic susceptibility $\tilde{\chi} = \chi' + i\chi''$ have been extensively studied. The imaginary part of the susceptibility, χ'' , is proportional to the dissipation in the sample. In macroscopic type II superconductors, the ac dissipation increases with magnetic field, proportional to the vortex density. Very recently, there has been an interest in the study of mesoscopic superconductors where the sample dimensions are of the order of the London penetration depth². In this work we will show that in mesoscopic superconductors the ac dissipation has a non monotonous and oscillating dependence with magnetic field.

We first show the results of numerical simulations of mesoscopic squares

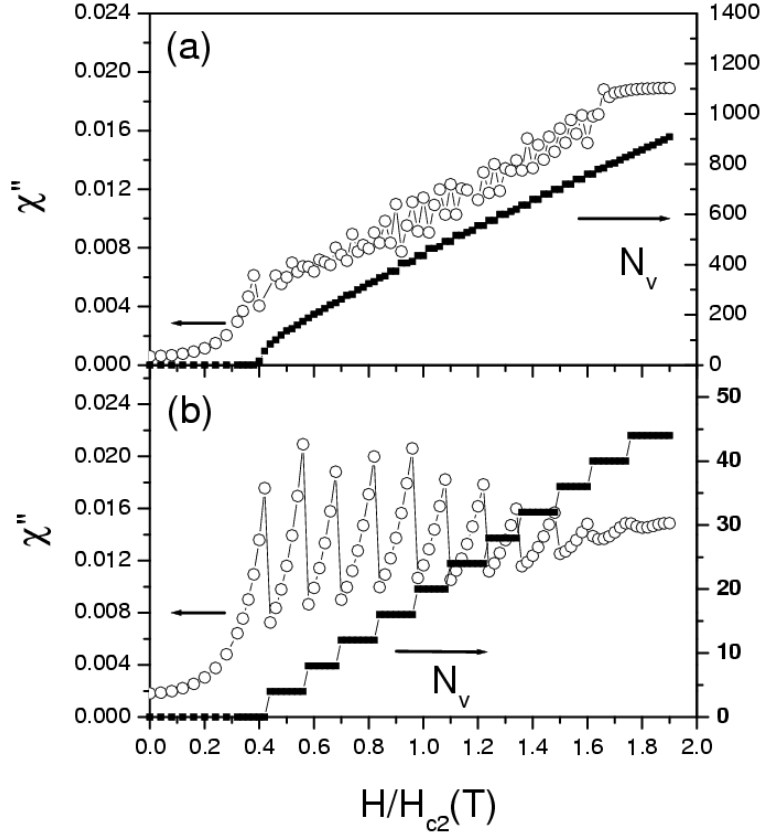


Fig. 1. ac dissipation, χ'' , and number of vortices, N_v , vs. magnetic field H . (a) Large sample, $40\lambda \times 40\lambda$. (b) Mesoscopic sample, $10\lambda \times 10\lambda$

using the time-dependent Ginzburg-Landau (TDGL) equations:^{3,4}

$$\frac{\partial \Psi}{\partial t} = \frac{1}{\eta} [(\nabla - i\mathbf{A})^2 \Psi + (1 - T)(1 - |\Psi|^2)\Psi] \quad (1)$$

$$\frac{\partial \mathbf{A}}{\partial t} = (1 - T) \text{Im}[\Psi^*(\nabla - i\mathbf{A})\Psi] - \kappa^2 \nabla \times \nabla \times \mathbf{A} \quad (2)$$

where Ψ and $\mathbf{A}$ are the order parameter and vector potential respectively and T is the temperature. Lengths are normalized by the coherence length $\xi(0)$, times by $t_0 = 4\pi\sigma_n\lambda_L^2/c^2$, $\mathbf{A}$ by $H_{c2}(0)\xi(0)$, T by T_c ; and we have $\eta = c^2/(4\pi\sigma_n\kappa^2D)$. The boundary conditions are $(\nabla - i\vec{A})^\perp \Psi = 0$ and $B_z|_S = (\nabla \times \mathbf{A})_z|_S = H_z^{ext}$. We consider an ac+dc magnetic field: $H_z^{ext} = H_{dc} + h_{ac} \cos(\omega t)$ with $h_{ac} \ll H_{dc}$. The magnetization is given by $4\pi M(t) = \langle B(t) \rangle - H(t)$, with $\langle B(t) \rangle$ averaged over the sample. The ac magnetic susceptibilities are obtained as $\chi' = \frac{1}{\pi h_{ac}} \int_0^{2\pi} M(t) \cos(\omega t) d(\omega t)$ and $\chi'' =$

Mesoscopic superconductors

$\frac{1}{\pi h_{ac}} \int_0^{2\pi} M(t) \sin(\omega t) d(\omega t)$. We consider here $\kappa = 2$, $T = 0.5$ and the parameter $\eta = 12$. We use a finite difference discretization scheme^{3,4} with $\Delta x = \Delta y = 0.5\xi$ and time step $\Delta t \leq 0.015t_0$. Fig. 1(a) shows $\chi''(H_{dc})$ at $\omega = 0.06\nu_o$ obtained in a “large” sample of $40\lambda \times 40\lambda$. We also show in Fig.1(a) the number of vortices as a function of H_{dc} . At small H_{dc} , in the Meissner state, χ'' increases continuously with increasing H_{dc} . In this case, the magnetic field induces static supercurrents which deplete the order parameter at the boundary and this leads to an increase of dissipation for increasing H_{dc} . Above a penetration field $H_p > H_{c1}$ (there is a surface barrier⁴) vortices enter into the sample and the dissipation increases linearly with the number of vortices. In Fig. 1(b) we show the similar case but for a mesoscopic square of size $10\lambda \times 10\lambda$. When the magnetic field is increased above the first penetration field $H_p \equiv H_{p1}$, the first vortices enter into the sample, and we see that there is a discontinuous jump in χ'' with a *decrease* of dissipation just at H_p . Further jumps in $\chi''(H_{dc})$ are present at the other magnetic fields for vortex penetration, $H_{p2}, H_{p3}, \dots$, where χ'' *decreases*. The jumps are followed by a later continuous increase of $\chi''(H_{dc})$ with increasing H_{dc} while the number of vortices N_v remains fixed. This increase of dissipation at fixed N_v has been interpreted as due to “nascent vortices”⁴ which give a large fluctuation of $|\Psi|$ at the boundary. Later, when vortices enter, there is a sudden decrease of the ac losses.

We now discuss the experimental measurements. An array of 200×250 Pb squares were deposited by thermal evaporation on a silicon substrate. The squares of $L = 1.3 \mu\text{m}$ on side and $d = 300\text{\AA}$ thick were defined by e-beam lithography and a subsequent lift-off. This thickness d corresponds to an effective $\kappa_{eff} = \kappa_{Pb}^2 \xi_{Pb} / d \approx 1.3$ and to a length $L \approx 10\lambda_{eff}$. A SEM image of part of the sample is shown in the lower inset of Fig. 2. Magnetic resonance measurements have been made with a commercial Bruker ESP 300 spectrometer. Spectra were acquired at 9.5 GHz (X-Band) using a TE102 rectangular cavity. The external magnetic field was modulated with a 100 kHz ac field of varying amplitude to obtain the field derivative of the microwave absorption ($d\chi''/dH$). Low temperature measurements were made using a continuous flow helium cryostat. The sample was positioned inside the cavity with the dc field and the rf field perpendicular and parallel to the film plane, respectively. Spectra features were generally of very weak intensity and it was necessary to use long acquisition times (several minutes) in order to obtain a reasonably good signal to noise ratio. In this way, spectra of $d\chi''/dH$ vs. H were obtained. Fig. 2 shows the integrated curve, which is proportional to χ'' , as function of the the magnetic field H for a temperature $T = 4.5K$. We first observe an overall increase of χ'' with H which is also observed in bulk *Pb* and it is due to microscopic mechanisms (not described

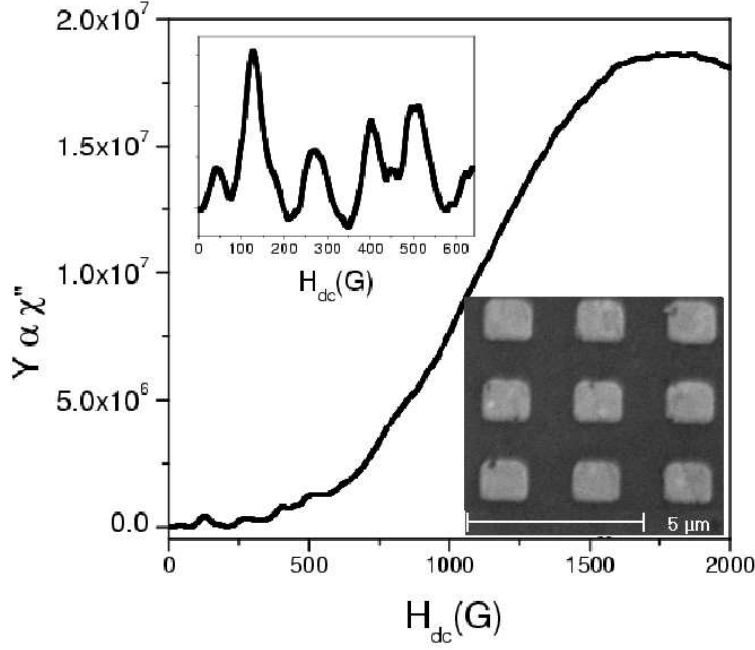


Fig. 2. Measured ac susceptibility, $Y \propto \chi''$, in 1.3μ Pb squares at 9.5 GHz. Lower inset: SEM image of part of the sample.

by the TDGL equations). An enhancement of the behavior of χ'' at low fields is shown in the upper inset of Fig. 2. We see that the ac dissipation has a non monotonous oscillatory behavior as a function of H . This is in qualitative agreement with the theoretical result of Fig. 1(b). Effects of disorder due to small variations in the shape of the squares may cause that the oscillations of χ'' are not as uniform as in Fig. 1(b). In conclusion, we have observed that in mesoscopic squares the dependence of ac dissipation with magnetic field is very sensitive to vortex entrance events.

We acknowledge support from Fundación Antorchas, SECYT-CITMA international cooperation agreement, CLAF and ANPCyT.

REFERENCES

1. M. W. Coffey and J. R. Clem, *Phys. Rev. Lett.* **67**, 386 (1991).
2. V. A. Shweigert, F. M. Peeters, and P. S. Deo, *Phys. Rev. Lett.* **81**, 2783 (1998).
3. R. Kato, Y. Enomoto, and S. Maekawa, *Phys. Rev. B* **47**, 8016 (1993).
4. A. D. Hernández and D. Domínguez, *Phys. Rev. B* **65**, 144529 (2002); *Phys. Rev. B* **66**, 144505 (2002).